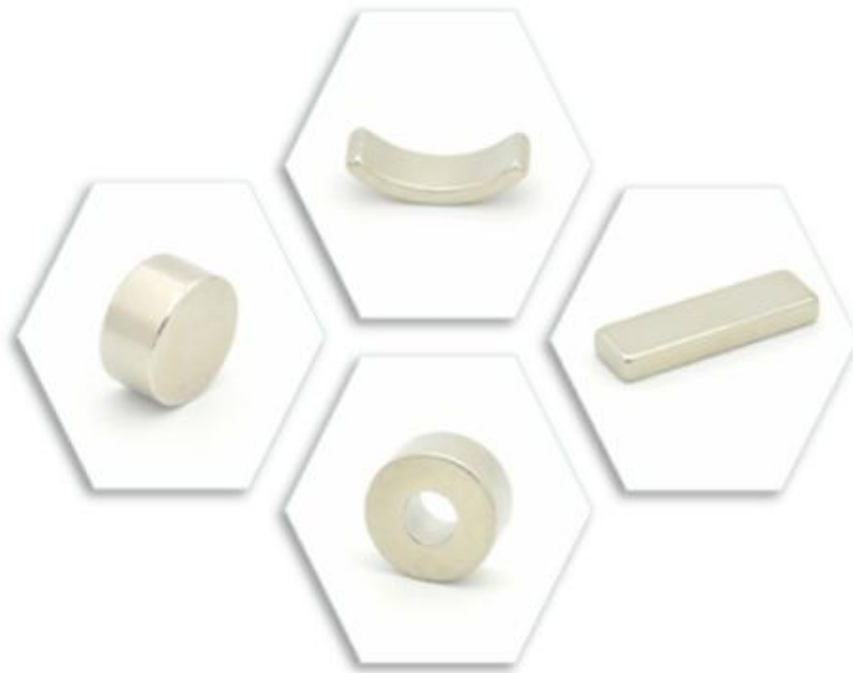


Sintered NdFeB Magnets' Specifications



Chengdu Heaven and Great Technology Co.,Ltd

📍 146 Hongqi Road, Pidu District, Chengdu, China

☎ +86 028 69914836

✉ mago@advancedmagnets.com

🌐 www.advancedmagnets.com

Table I Sintered NdFeB Grades and Their Magnetic Properties

Grade	B_r		H_{cb}		H_{cj}		$(BH)_{max}$		T_w		
	kGs	T	kOe	kA/m	kOe	kA/m	MGOe	kJ/m^3	$^{\circ}\text{C}$		
N52	14.2-14.8	1.42-1.48	≥ 10.5	≥ 836	≥ 11	≥ 876	50-53	398-422	≤ 80		
N50	13.9-14.4	1.39-1.44	≥ 10.8	≥ 859	≥ 12	≥ 955	48-51	382-406			
N48	13.6-14.1	1.36-1.41	≥ 11.6	≥ 923			46-49	366-390			
N45	13.2-13.7	1.32-1.37	≥ 11.6	≥ 923			43-46	342-366			
N42	12.8-13.3	1.28-1.33	≥ 11.4	≥ 907			40-43	318-342			
N40	12.4-12.9	1.24-1.29	≥ 11.4	≥ 907			38-41	302-326			
N38	12.1-12.6	1.21-1.26	≥ 11.2	≥ 891			36-39	286-310			
N35	11.7-12.2	1.17-1.22	≥ 10.8	≥ 859			33-36	263-286			
N33	11.3-11.8	1.13-1.18	≥ 10.5	≥ 836			31-34	247-271			
N30	10.8-11.3	1.08-1.13	≥ 10.0	≥ 796			28-31	223-247			
N50M	13.9-14.4	1.39-1.44	≥ 13.0	≥ 1035			≥ 13	≥ 1035		48-51	382-406
N48M	13.6-14.1	1.36-1.41	≥ 12.8	≥ 1019			≥ 14	≥ 1114	46-49	366-390	
N45M	13.2-13.7	1.32-1.37	≥ 12.5	≥ 995	43-46	342-366					
N42M	12.8-13.3	1.28-1.33	≥ 12.0	≥ 955	40-43	318-342					
N40M	12.4-12.9	1.24-1.29	≥ 11.6	≥ 923	38-41	302-326					
N38M	12.1-12.6	1.21-1.26	≥ 11.3	≥ 899	36-39	286-310					
N35M	11.7-12.2	1.17-1.22	≥ 10.9	≥ 867	33-36	263-286					
N33M	11.3-11.8	1.13-1.18	≥ 10.5	≥ 836	31-34	247-271					
N30M	10.8-11.3	1.08-1.13	≥ 10.0	≥ 796	28-31	223-247					
N50H	13.9-14.4	1.39-1.44	≥ 13.0	≥ 1035	≥ 16	≥ 1273	48-51	382-406	≤ 120		
N48H	13.6-14.1	1.36-1.41	≥ 12.8	≥ 1019	≥ 17	≥ 1353	46-49	366-390			
N45H	13.2-13.7	1.32-1.37	≥ 12.5	≥ 995			43-46	342-366			
N42H	12.8-13.3	1.28-1.33	≥ 12.0	≥ 955			40-43	318-342			
N40H	12.4-12.9	1.24-1.29	≥ 11.6	≥ 923			38-41	302-326			
N38H	12.1-12.6	1.21-1.26	≥ 11.3	≥ 899			36-39	286-310			
N35H	11.7-12.2	1.17-1.22	≥ 10.9	≥ 867			33-36	263-286			
N33H	11.3-11.8	1.13-1.18	≥ 10.5	≥ 836			31-34	247-271			
N30H	10.8-11.3	1.08-1.13	≥ 10.0	≥ 796			28-31	223-247			
N48SH	13.6-14.1	1.36-1.41	≥ 12.8	≥ 1019			≥ 20	≥ 1592	46-49	366-390	≤ 150
N45SH	13.2-13.7	1.32-1.37	≥ 12.5	≥ 995	43-46	342-366					
N42SH	12.8-13.3	1.28-1.33	≥ 12.0	≥ 955	40-43	318-342					
N40SH	12.4-12.9	1.24-1.29	≥ 11.6	≥ 923	38-41	302-326					
N38SH	12.1-12.6	1.21-1.26	≥ 11.3	≥ 899	36-39	286-310					
N35SH	11.7-12.2	1.17-1.22	≥ 10.9	≥ 867	33-36	263-286					
N33SH	11.3-11.8	1.13-1.18	≥ 10.5	≥ 836	31-34	247-271					
N30SH	10.8-11.3	1.08-1.13	≥ 10.0	≥ 796	28-31	223-247					

Grade	B_r		H_{cb}		H_{cj}		$(BH)_{max}$		T_w
	kGs	T	kOe	kA/m	kOe	kA/m	MGOe	kJ/m^3	°C
N42UH	12.8-13.3	1.28-1.33	≥ 12.2	≥ 971	≥ 25	≥ 1990	40-43	318-342	≤ 180
N40UH	12.4-12.9	1.24-1.29	≥ 11.8	≥ 939			38-41	302-326	
N38UH	12.1-12.6	1.21-1.26	≥ 11.5	≥ 915			36-39	286-310	
N35UH	11.7-12.2	1.17-1.22	≥ 11.1	≥ 883			33-36	263-286	
N33UH	11.3-11.8	1.13-1.18	≥ 10.7	≥ 851			31-34	247-271	
N30UH	10.8-11.3	1.08-1.13	≥ 10.2	≥ 812			28-31	223-247	
N40EH	12.4-12.9	1.24-1.29	≥ 11.8	≥ 939	≥ 30	≥ 2388	38-41	302-326	≤ 200
N38EH	12.1-12.6	1.21-1.26	≥ 11.5	≥ 915			36-39	286-310	
N35EH	11.7-12.2	1.17-1.22	≥ 11.1	≥ 883			33-36	263-286	
N33EH	11.3-11.8	1.13-1.18	≥ 10.7	≥ 851			31-34	247-271	
N30EH	10.8-11.3	1.08-1.13	≥ 10.2	≥ 812			28-31	223-247	
N35AH	11.7-12.2	1.17-1.22	≥ 11.1	≥ 883	≥ 35	≥ 2786	33-36	263-286	≤ 230
N33AH	11.3-11.8	1.13-1.18	≥ 10.7	≥ 851			31-34	247-271	
N30AH	10.8-11.3	1.08-1.13	≥ 10.2	≥ 812			28-31	223-247	
N28AH	10.4-10.9	1.04-1.09	≥ 9.8	≥ 780			26-29	207-231	

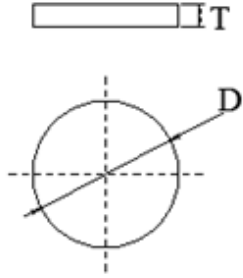


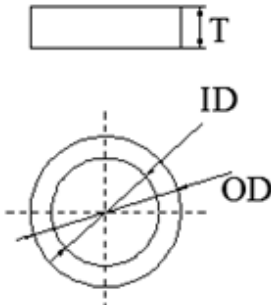



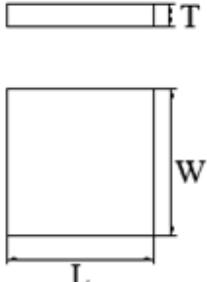

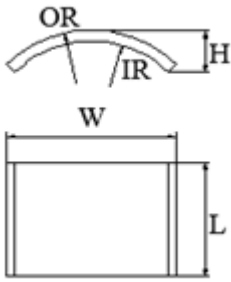


Note:

* The data in the above table were samples' results tested at the temperature of 20 °C.

* The temperature coefficients of B_r and H_{cj} are $\alpha(B_r)$: -0.09~-0.12 %/°C and $\beta(H_{cj})$: -0.40~-0.60 %/°C, respectively.

* The above data are only for reference, magnets can be tailored according to customers' personalized requirements.

Table II Sintered NdFeB Magnets' Shapes, Magnetization Direction and Size Range

Shape	Graphic Description	Magnetization Direction		Size Range
Disc/Cylinder			Axially Magnetized	D: 1-100 mm T: 0.3-100 mm
			Diametrically Magnetized	D: 1-100 mm T: 0.3-100 mm
Ring			Axially Magnetized	OD: 1.5-100 mm ID: 0.5-90 mm T: 0.5-60 mm
			Diametrically Magnetized	OD: 1.5-100 mm ID: 0.5-90 mm T: 0.5-60 mm
			Radially Magnetized	OD: 20-200 mm ID: 10-180 mm T: 0.5-60 mm
Block/ Rectangular			Thickness Magnetized	L: 1-160 mm W: 0.5-100 mm T: 0.3-100 mm
Arc/Segment			Diametrically Magnetized	OD-ID \geq 1 mm L: 1-160 mm W: 3-100 mm H: 1-80 mm
			Radially Magnetized	OD-ID \geq 1 mm L: 1-80 mm W: 3-40 mm H: 1-10 mm

Note:

* Other shapes of sintered NdFeB magnets can also be tailored according to customers' specific requirements.

Table III Sintered NdFeB Magnets' Coating Types

Coating	Thickness (μm)	SST (hr)	PCT (hr)	T_w ($^{\circ}\text{C}$)
Zn (Zinc)	5-15	>24	-	≤ 160
C-Zn (Colored Zinc)	5-15	>48	-	≤ 160
Electroless Nickel	10-30	>96	>72	≤ 230
NiCuNi (Nickel Copper Nickel)	10-20	>48	>48	≤ 230
NiCu + Black Nickel	10-20	>48	>72	≤ 230
NiCuNi + Tin	10-25	>48	>48	≤ 160
NiCuNi + Gold	10-25	>48	>48	≤ 230
NiCuNi + Silver	10-25	>48	>48	≤ 160
Epoxy	10-30	>72	>48	≤ 160
Teflon	10-20	>96	-	≤ 230
Everlube	10-20	>96	>72	≤ 230
Parylene	0.2-5	>96	-	≤ 230

Note:

* Salt spray test (SST) was conducted at 35 $^{\circ}\text{C}$ with 5% NaCl solution.

* Pressure cooker test (PCT) was conducted at 120 $^{\circ}\text{C}$, 2 atm and 100% RH.

Table IV Some Physical Properties of Sintered NdFeB Magnets

Parameter	Unit	Value
Density (ρ)	g/cm^3	7.4-7.7
Curie Temperature (T_c)	$^{\circ}\text{C}$	310-370
Recoil Permeability (μ_{rec})	-	1.05
Vickers Hardness (HV)	MPa	500-600
Bending Strength (σ_{bb})	MPa	200-400
Compressive Strength (σ_{bc})	MPa	1000-1100
Tensile Strength (σ_{b})	MPa	80-90
Resistivity (ρ)	$\mu\Omega\cdot\text{m}$	1.4-1.6
Thermal Conductivity (λ)	$\text{W}/(\text{m}\cdot\text{K})$	8-10
Young's Modulus (E)	GPa	150-200
Thermal Expansivity // Magnetization ($\alpha_{//}$)	$10^{-6}/^{\circ}\text{C}$	3-4
Thermal Expansivity \perp Magnetization (α_{\perp})	$10^{-6}/^{\circ}\text{C}$	1-3

Note:

* The above data are only for reference, specific magnets maybe have different values.